


Showcasing research from Prof. Quan Yuan's laboratory, College of Chemistry and Molecular Sciences, Wuhan University, China

A vitamin-responsive mesoporous nanocarrier with DNA aptamer-mediated cell targeting

A smart nanocarrier for targeted drug delivery is reported. Drugs are locked in the nanocarrier just like treasures locked in a box, while intracellular vitamin H acts as the key to open the nanocarrier for drug release and killing the target cells.

As featured in:

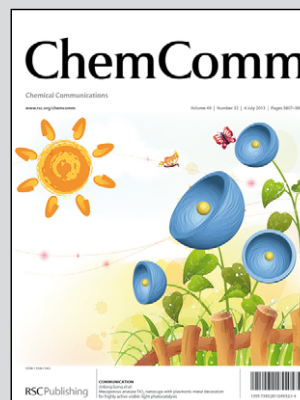

See Quan Yuan,
Dai-Wen Pang, Yi Lu *et al.*,
Chem. Commun., 2013, **49**, 5823.

RSC Publishing

www.rsc.org/chemcomm

Registered Charity Number 207890

A vitamin-responsive mesoporous nanocarrier with DNA aptamer-mediated cell targeting†

Cite this: *Chem. Commun.*, 2013, **49**, 5823

Received 7th February 2013,
Accepted 4th April 2013

DOI: 10.1039/c3cc41072b

www.rsc.org/chemcomm

Le-Le Li,^{†,ab} Mengying Xie,^{†,a} Jie Wang,^a Xinyang Li,^a Cheng Wang,^a Quan Yuan,^{*a} Dai-Wen Pang,^{*a} Yi Lu^{*b} and Weihong Tan^{cd}


A smart drug delivery system with cancer cell targeting and bioresponsive controlled drug release has been constructed by taking advantage of a protein-capped mesoporous nanovalve and a DNA aptamer.

A major challenge in current cancer therapeutics is the targeted delivery of cancer drugs into disease cells more efficiently while mitigating harmful side effects. This challenge is being met by the development of anti-cancer cell agents to achieve targeted drug delivery systems. Among them, anticell aptamers are single-stranded DNA or RNA molecules that can fold into a three-dimensional structure to bind with a certain type of cancer cells.¹ The high cell-binding affinity and selectivity, low immunogenicity, fast tissue penetration, rapid systemic clearance, and small size make aptamers excellent recognition elements for targeted delivery of therapeutics.²

In addition to targeting, the ability to induce triggerable delivery of anticancer drugs is another important factor to consider for the spatiotemporal control over the delivery of chemotherapeutic agents. Such “on-demand” controlled release systems could regulate the time and the site of drug delivery more precisely and thus increase drug retention in cancers. The ideal drug delivery system will combine cancer cell targeting with subsequent intracellular triggerable controlled drug release to maximize cancer killing and minimize metastatic spread. Recently, mesoporous silica nanoparticles (MSNs) have received increased attention as nanocarriers for the controlled release of therapeutics due to their

outstanding structural characteristics.^{3,4} Despite the successes, internal stimuli used for the controlled-release systems and the mechanism by which the release is controlled are still limited. Furthermore, a main challenge for MSN-based triggerable nanovalves is to achieve simultaneous targeting and drug release, which often requires coupling of the targeting group with the capping group on the limited surface sites of the same nanoparticle.

Known as biotin as well as coenzyme R, vitamin H is a member of the B vitamin complex family, which acts as a growth promoter of all cells.⁵ Recently, it has been shown that the vitamin H content in cancer cells is substantially higher than that in normal tissues.⁶ Herein we report a novel method of taking advantage of different affinities of desthiobiotin and vitamin H toward avidin and combining the targeting ability of an aptamer to develop a new generation of MSN-based nanovalves for simultaneous targeted drug delivery and intracellular triggerable drug release. As shown in Scheme 1,

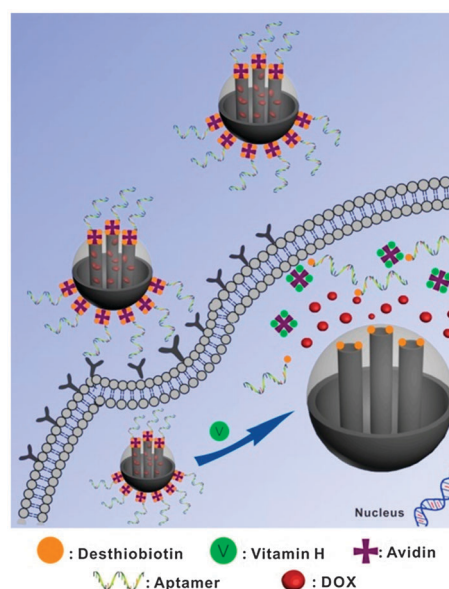

Scheme 1 Schematic illustration of vitamin-responsive release system for targeted cancer therapy guided by an aptamer.

^a Key Laboratory of Analytical Chemistry for Biology and Medicine (Ministry of Education), College of Chemistry and Molecular Sciences, Wuhan University, Wuhan 430072, China. E-mail: yuanquan@whu.edu.cn, dwpang@whu.edu.cn

^b Department of Chemistry, University of Illinois at Urbana-Champaign, Urbana, IL 61801, USA. E-mail: yi-lu@illinois.edu

^c Department of Chemistry and Department of Physiology and Functional Genomics, Shands Cancer Center and UF Genetics Institute, Center for Research at the Bio/Nano Interface, University of Florida, Gainesville, Florida 32611-7200, USA

^d State Key Laboratory for Chemo/Bio-Sensing and Chemometrics, College of Biology, and College of Chemistry and Chemical Engineering, Hunan University, Changsha 410082, China

† Electronic supplementary information (ESI) available: Experimental details and supplementary results. See DOI: 10.1039/c3cc41072b

‡ These authors contributed equally to this work.

the MSN was selected as the inorganic scaffold to load with guest molecules, and the external surface was modified with desthiobiotin molecules. Then the pores were capped by avidin proteins through strong desthiobiotin-avidin interaction. Furthermore, a cancer cell-specific DNA aptamer was attached to the avidin on the surface of MSNs to result in the final nanocarriers. Due to the selective targeting ability of the aptamers on the surface of MSN-Avi-Apt, the loaded nanocarriers can specifically target and then enter cancer cells through receptor-mediated endocytosis. Since the pores of MSN-Avi-Apt are capped, there is less premature leakage of drugs during the delivery process. Upon entering the target cancer cells, MSN-Avi-Apt will be uncapped by intracellular vitamin H biomolecules, accelerating the release of drugs from nanocarriers and the killing of target cancer cells.

The prepared MSNs (*ca.* 150 nm) with a typical hexagonal channel-like mesoporous structure were confirmed using TEM, SEM, X-ray diffraction and nitrogen adsorption-desorption isotherms (Fig. S1–S4, ESI[†]). The outlet of mesoporous silica was modified with amine groups and then conjugated with desthiobiotin molecules through EDC/sulfo-NHS coupled reactions. The efficient attachment of desthiobiotin onto MSNs was validated by the appearance of a broad absorption band at around 1680 cm^{-1} in the FTIR spectra that can be assigned to vibrations of the cyclic-urea group within the attached desthiobiotin molecules (Fig. S5, ESI[†]). For preparation of the gated material (MSN-Avi), avidin was added to cap the pores through the formation of a desthiobiotin-avidin complex (Fig. S1a, ESI[†]). To simultaneously provide cancer-targeting capability to the avidin-capped MSNs, we chose a 41-mer DNA aptamer *sgc8* as the targeting aptamer for further functionalization. *sgc8* has been shown to be highly specific in binding to cell membrane receptor protein tyrosine kinase 7 (PTK 7),⁷ a protein that is overexpressed on the plasma membrane of CCRF-CEM cells (CEM), a human precursor T-cell acute lymphoblastic leukemia (T-ALL) cell line.⁸ In addition, the *sgc8* aptamer was labeled with a desthiobiotin group at the 5'-end to allow attaching onto the avidins on the surface of MSN-Avi to give final nanocarriers MSN-Avi-Apt. Zeta potential measurements (Fig. S6, ESI[†]) showed that the MSN-Avi-Apt nanocarriers were highly negatively charged. The amount of DNA conjugation was determined to be $0.4\text{ }\mu\text{mol g}^{-1}\text{ SiO}_2$ using UV/Vis spectroscopy.

The intracellular release of the entrapped drugs is related to a highly effective displacement reaction involving the presence of vitamin H biomolecules in the cancer cells (Fig. 1a). The association constant (K_a) of vitamin H toward avidin ($\sim 1 \times 10^{15}\text{ M}^{-1}$)^{9,10} is ~ 20 -fold higher than that of desthiobiotin toward avidin molecules ($5 \times 10^{13}\text{ M}^{-1}$),¹¹ which is the working principle of our vitamin-responsive nanovalves through effective dissociation reaction by displacement. To investigate the target-triggered controlled release property of the ensemble, rhodamine 640 (denoted as Rh640) was used as a model guest molecule and was loaded into the pores of MSN-Avi-Apt. The uncapping and subsequent release of the dye was monitored through the measurement of the absorbance maximum of Rh640 (553 nm) in solution as a function of time. As shown in Fig. 1b, the nanogated nanocarriers exhibited negligible leakage of the entrapped dye molecules during the first 200 min in the absence of a target, thus indicating good end-capping efficiency. When vitamin H molecules were added to the

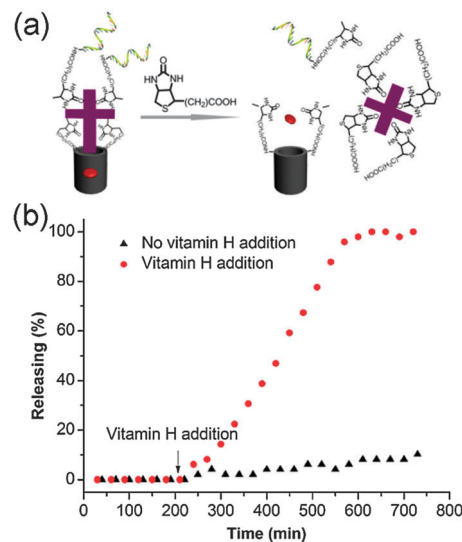


Fig. 1 (a) Schematics of vitamin-responsive drug release process for the nanovalves. (b) Release curve for MSN-Avi-Apt with and without vitamin H addition. Data have been normalized to the maximum level of dye released in the experiment.

suspension, a fast release of dye molecules occurred due to effective competitive binding. Interestingly, the release curve shows a fairly slow release for the first 100 min after the addition of vitamin H. This result can be explained by the replacement reaction process, in which four vitamin H molecules bind with one capped avidin for effective uncapping. After 100 min, the capping proteins are effectively replaced, leading to a faster release of Rh 640. This release curve compares well with the feather of the reported protein-capped MSN system.^{4b} In contrast, only slight leaking of dye molecules (less than 10%) from the nanogated nanocarriers occurred even after 10 h of incubation without vitamin H exposure, demonstrating the stable capping capability of the nanovalves.

To test the targeting specificity of the nanocarriers, we incubated MSN-Avi and MSN-Avi-Apt with CEM cells at $37\text{ }^{\circ}\text{C}$ for 2 h. Subsequent analysis using confocal microscopy (Fig. 2a) revealed that CEM cells incubated with MSN-Avi-Apt bearing the *sgc8* aptamer showed strong fluorescence within the cancer cells, while the nanocarriers MSN-Avi without aptamer attachment gave rise to less fluorescence in the CEM cells (Fig. 2b), confirming the role of the specific aptamer in cell binding and the endocytosis-based internalization mechanism. To further confirm the aptamer-mediated targeting specificity, we performed similar experiments using Ramos cells with no receptor protein PTK 7 on the membrane as control cancer cells. Both MSN-Avi-Apt and MSN-Avi exhibit much less capability of cell-binding and internalization to Ramos cells (Fig. 2c and Fig. S7, ESI[†]), thus showing that the aptamer-modified nanocarriers have negligible binding affinity toward the non-target cells. The targeting specificity of the aptamer *sgc8* toward CEM cells was also confirmed using flow cytometry assays of the cells treated with a 6-carboxyfluorescein (FAM)-labeled *sgc8* (Fig. S8, ESI[†]). As shown in Fig. 2d and f, a 6-fold increase in mean fluorescence intensity was observed for CEM cells treated with the FAM-labeled MSN-Avi-Apt compared to the negative controls, but no obvious change was observed for Ramos cells (Fig. 2e and g).

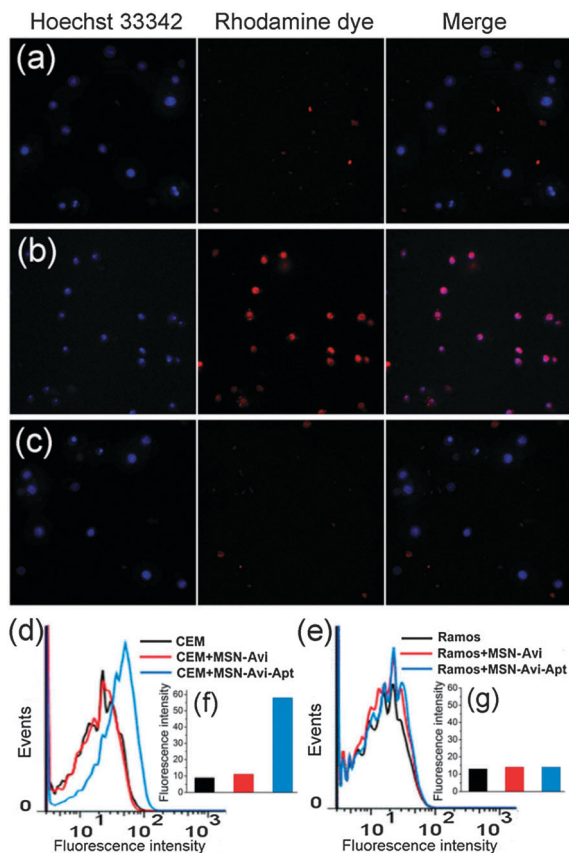


Fig. 2 Confocal microscopy images of (a) CEM cells treated with MSN-Avi, (b) CEM cells treated with MSN-Avi-Apt, and (c) Ramos cells treated with MSN-Avi-Apt. Flow cytometry analysis to monitor the binding of MSN-Avi-Apt and MSN-Avi with (d) CEM cells and (e) Ramos cells. The inset shows the corresponding histograms of the flow cytometric results of (f) CEM cells and (g) Ramos cells, respectively.

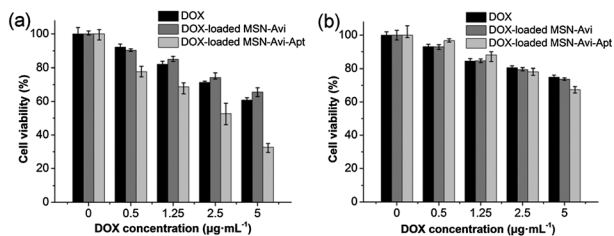


Fig. 3 Cytotoxicity assay of (a) CEM cells (target cells) and (b) Ramos cells (control cells) treated with DOX, DOX-loaded MSN-Avi, and DOX loaded MSN-Avi-Apt.

The *in vitro* cytotoxicities of the DOX-loaded nanocarriers were tested using MTT assay to evaluate their anti-cancer potential. Both cell lines treated with MSN-Avi or MSN-Avi-Apt alone showed negligible cell death even at a concentration of $200 \mu\text{g mL}^{-1}$ (Fig. S9, ESI[†]), indicating excellent biocompatibility of the nanocarriers. The loading content of DOX in MSN-Avi-Apt was found to be 1.7%. The DOX-loaded MSN-Avi-Apt also shows a vitamin-responsive drug release behavior (Fig. S10, ESI[†]). As shown in Fig. 3, DOX-loaded MSN-Avi-Apt showed significantly higher cytotoxicity to CEM cells as compared to DOX-loaded MSN-Avi and DOX alone. The cell viabilities were $32.7 \pm 6\%$ (mean \pm SD) for CEM cells treated with DOX-loaded MSN-Avi-Apt at DOX concentration of $5 \mu\text{g mL}^{-1}$, while the cell viabilities were $65.6 \pm 6\%$ and $60.8 \pm 4\%$ for cells treated with DOX-loaded MSN-Avi and DOX

alone at the same concentrations, respectively. The low cytotoxicity of DOX-loaded MSN-Avi is likely due to inefficient cellular uptake, which compared well with the cellular internalization studies. In contrast to the dramatic enhancement in cytotoxic effects of MSN-Avi-Apt on the CEM cells, a much less pronounced cytotoxicity of MSN-Avi-Apt toward the Ramos cells (cellular viability: $67.4 \pm 4\%$, $73.7 \pm 2\%$, and $74.9 \pm 4\%$ for three samples with the DOX concentration of $5 \mu\text{g mL}^{-1}$ respectively) was observed. Based on these data from the MTT assay, one can draw the conclusion that improved and selective cytotoxicity to target cancer cells can be achieved using the current smart nanocarriers, which can be attributed to three possible reasons: (1) the aptamer-functionalization enables the nanovalves to bind to and be internalized by CEM cells selectively, (2) the capping of the pores can alleviate the premature leakage of highly toxic anticancer drugs during the targeting process, (3) intracellular vitamin H-triggered drug release of the encapsulated drugs improves antiproliferative activity in cancer cells. Since the MSN-Avi-Apt was highly negatively charged, it is reasonable that the nanocarriers are able to escape from the endosome and to interact with the vitamin in cytoplasm.¹²

In conclusion, we demonstrate a smart drug delivery system with efficient cancer-specific delivery and intracellular controlled release of the drug. The *sgc8* aptamer serves as a model system to be conjugated with the MSN-based nanovalves for targeting specific cancer cells, while the pores were capped by the desthiobiotin-avidin complex to eliminate the premature drug leakage before they reach the specific sites. The vitamin H enables the opening of the nanovalves for intracellular controlled release of the entrapped drugs. The efficient cancer-cell-specific drug delivery of the nanovalves demonstrated a significant enhancement in the anticancer activity.

This work was supported by the National Natural Science Foundation of China (21201133, 51272186 to QY) and the U.S. National Institutes of Health (Grant ES016865 to YL). Q. Yuan thanks Wuhan University for start-up funds and large-scale instrument and equipment sharing foundation.

Notes and references

- 1 C. Tuerk and L. Gold, *Science*, 1990, **249**, 505; A. D. Ellington and J. W. Szostak, *Nature*, 1990, **346**, 818; X. Fang and W. Tan, *Acc. Chem. Res.*, 2010, **43**, 48.
- 2 H. Xing, N. Y. Wong, Y. Xiang and Y. Lu, *Curr. Opin. Chem. Biol.*, 2012, **16**, 429.
- 3 M. Vallet-Regí, F. Balas and D. Arcos, *Angew. Chem., Int. Ed.*, 2007, **46**, 7548; P. Yang, S. Gai and J. Lin, *Chem. Soc. Rev.*, 2012, **41**, 3679.
- 4 J. L. Vivero-Escoto, I. I. Slowing, C.-W. Wu and V. S.-Y. Lin, *J. Am. Chem. Soc.*, 2009, **131**, 3462; A. Schlossbauer, J. Kecht and T. Bein, *Angew. Chem., Int. Ed.*, 2009, **48**, 3092; J. Croissant and J. I. Zink, *J. Am. Chem. Soc.*, 2012, **134**, 7628.
- 5 B. Bowman and I. H. Rosenberg, *J. Nutr.*, 1987, **117**, 2121.
- 6 G. Russell-Jones, K. McTavish, J. McEwan, J. Rice and D. Nowotnik, *J. Inorg. Biochem.*, 2004, **98**, 1625.
- 7 K. Mossie, B. Jallal, F. Alves, I. Sures, G. D. Plowman and A. Ullrich, *Oncogene*, 1995, **11**, 2179.
- 8 D. Shangguan, Y. Li, Z. Tang, Z. C. Cao, H. W. Chen, P. Mallikaratchy, K. Sefah, C. J. Yang and W. Tan, *Proc. Natl. Acad. Sci. U. S. A.*, 2006, **103**, 11838.
- 9 W. Müller, H. Ringsdorf, E. Rump, G. Wildburg, X. Zhang, L. Angermaier, W. Knoll, M. Liley and J. Spinke, *Science*, 1993, **262**, 1706.
- 10 E.-L. Florin, V. T. Moy and H. E. Gaub, *Science*, 1994, **264**, 415.
- 11 M. Hoffmann, W. Müller, H. Ringsdorf, A. M. Rourke, E. Rump and P. A. Suci, *Thin Solid Films*, 1992, **210/211**, 780.
- 12 I. Slowing, B. G. Trewyn and V. S.-Y. Lin, *J. Am. Chem. Soc.*, 2006, **128**, 14792.